

# Tecnoflon® P 757

## Peroxide Curable Terpolymer

Tecnoflon® P 757 is a medium viscosity, medium fluorine (67%), peroxide curable fluoroelastomer. Tecnoflon® P 757 exhibits superior resistance to a wide variety of chemicals, coupled with excellent processability, optimum compression set and good flexibility at low temperatures. Tecnoflon® P 757 can be cross-linked using organic peroxides in conjunction with a coagent.

Some of the basic properties of Tecnoflon® P 757 are:

- Low post cure
- Superior mold flow
- Lack of mold fouling
- Excellent mold release
- Good chemical resistance
- Good stress relaxation
- Good metal bonding
- Good low temperature performance
- FDA compliant

Tecnoflon® P 757 can be used for compression, injection and transfer molding of shaft seals, valve seals, O-rings, gaskets or any item requiring superior

chemical resistance. Tecnoflon® P 757 can be combined with the cure system and other typical fluoroelastomer compounding ingredients. Mixing can be accomplished with two roll mills or internal mixers.

Tecnoflon® P 757 can be extruded into hoses or profiles and can be calendered to make sheet stocks or belting. Finished goods may be produced by a variety of rubber processing methods.

Tecnoflon® P 757 is registered in the FDA Inventory of Effective Premarket Notifications for Food Contact Substances. It can be compounded so that the finished gaskets or seals can be used in food processing equipments (see “food processing compounds” section on pages 9 and 10).

### Handling and safety

Normal care and precautions should be taken to avoid skin contact, eye contact and breathing of fumes. Smoking is prohibited in working areas. Wash hands before eating or smoking. For complete health and safety information, please refer to the safety data sheet.

### Basic characteristics of the raw polymer are as follows:

Property	Typical Value	Unit	Test Method
ML (1+10') at 121 °C	44	MU	ASTM D1646
Fluorine content	67	%	Solvay Internal Method – NMR
Specific gravity	1.83	g/cm <sup>3</sup>	ASTM D792
Color	Translucent		
Packaging / Form	Slabs		
Solubility	Ketones and esters		

### Typical properties

Test Compound	Typical Value	Unit	Test Method
<b>Tecnoflon® P 757</b>	100	phr	
Luperox® 101XL-45	3	phr	
Drimix® TAIC (75%)	4	phr	
ZnO	5	phr	
N-990 MT Carbon Black	30	phr	

# Tecnoflon® P 757

## Peroxide Curable Terpolymer

Property	Typical Value	Unit	Test Method
Mooney viscosity ML (1+10') at 121 °C	50	MU	ASTM D1646
<b>Mooney Scorch MS 135 °C</b>			ASTM D1646
MV	22	MU	
t <sub>15</sub>	12.1	min	
<b>ODR 12 min at 177 °C arc 3°</b>			ASTM D2084
Minimum torque	10.6	lb·in	
Maximum torque	129	lb·in	
t <sub>s2</sub>	1.1	min	
t' <sub>50</sub>	1.7	min	
t' <sub>90</sub>	2.1	min	
<b>MDR 6 min at 177 °C arc 0.5°</b>			ASTM D6601
Minimum torque	1.21	lb·in	
Maximum torque	24.1	lb·in	
t <sub>s2</sub>	0.4	min	
t' <sub>50</sub>	0.6	min	
t' <sub>90</sub>	0.9	min	
<b>MDR 12 min at 170 °C arc 0.5°</b>			ASTM D6601
Minimum torque	1.28	lb·in	
Maximum torque	23.7	lb·in	
t <sub>s2</sub>	0.6	min	
t' <sub>50</sub>	1.0	min	
t' <sub>90</sub>	2.0	min	
<b>Press cure: 6 min at 170 °C</b>			
100% Modulus	3.2	MPa	ASTM D412C
Tensile strength	16.7	MPa	
Elongation at break	320	%	
Hardness	68	ShoreA	ASTM D2240
<b>Post cure: 4 h at 230 °C</b>			
100% Modulus	4.9	MPa	ASTM D412C
Tensile strength	23.4	MPa	
Elongation at break	290	%	
Hardness	71	ShoreA	ASTM D2240
<b>Compression set</b>			ASTM D395 method B
25% deformation, 70 h at 200 °C			
O-ring #214	22	%	
6 mm buttons	15	%	


# Tecnoflon® P 757

Peroxide Curable Terpolymer


## Effect of curative levels

Property	Typical Value	Unit	Test Method
Tecnoflon® P 757	100	phr	
Luperox® 101XL-45	See picture	phr	
Drimix® TAIC (75%)	See picture	phr	
ZnO	5	phr	
N-990 MT Carbon Black	30	phr	

### $\Delta$ torque (MH-ML) [lb·in]

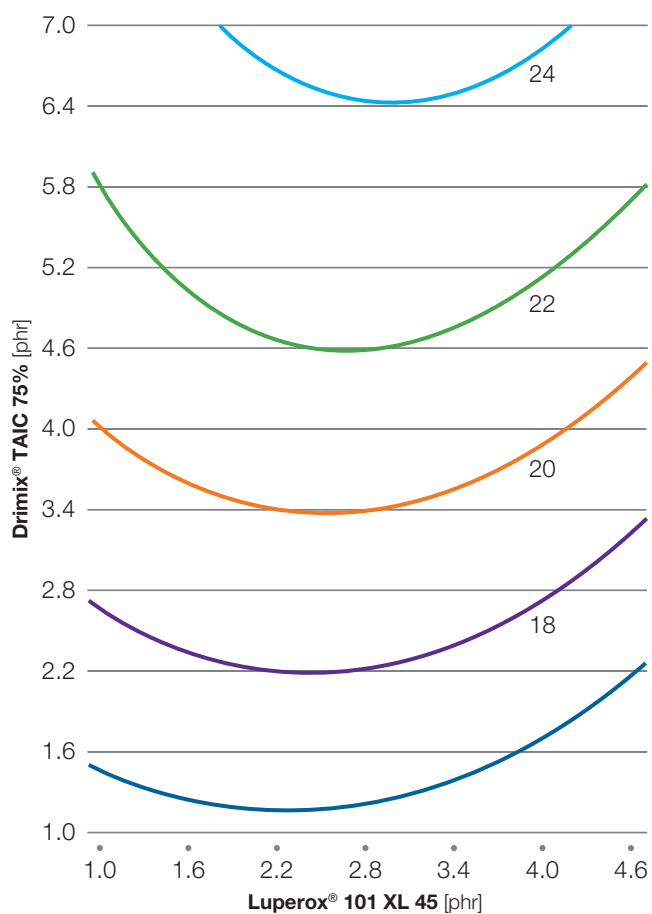

### Curing rate (MH-ML)/(t'90-t's2) [lb·in/s]

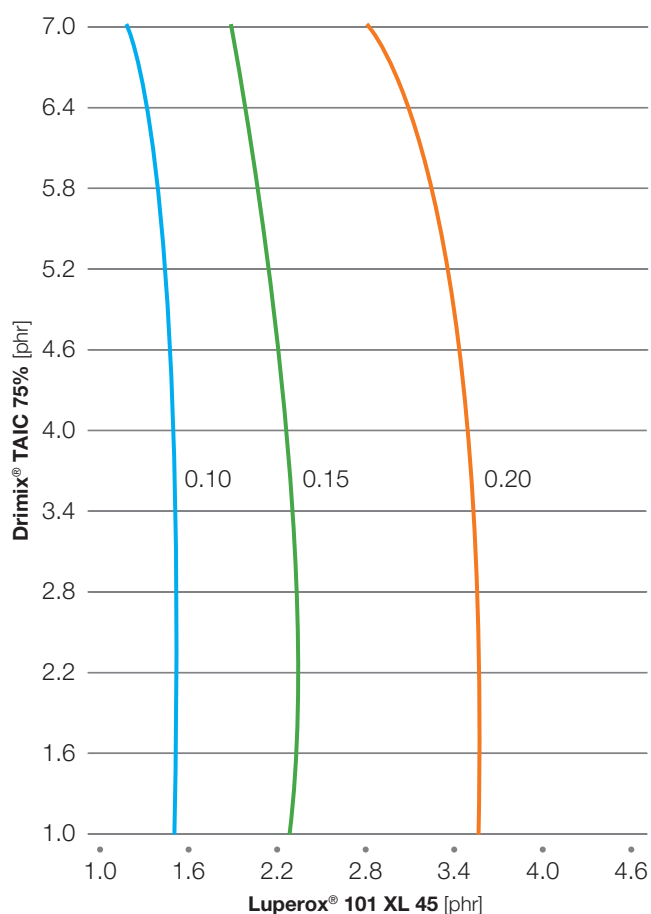


# Tecnoflon® P 757


Peroxide Curable Terpolymer

## Mechanical properties after post cure 4 h at 230 °C

### Modulus 100% [MPa]

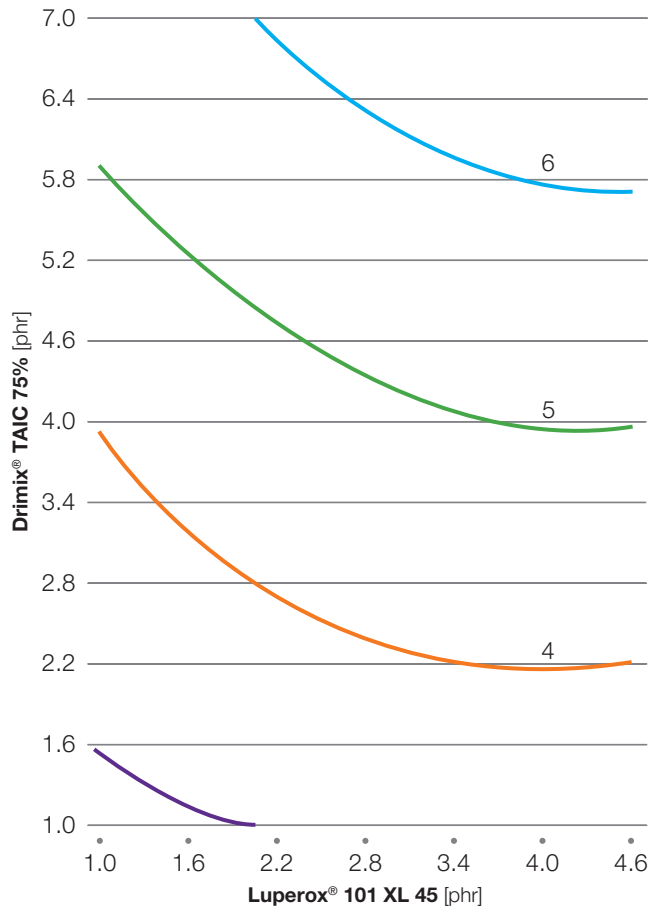


### Tensile strength [MPa]

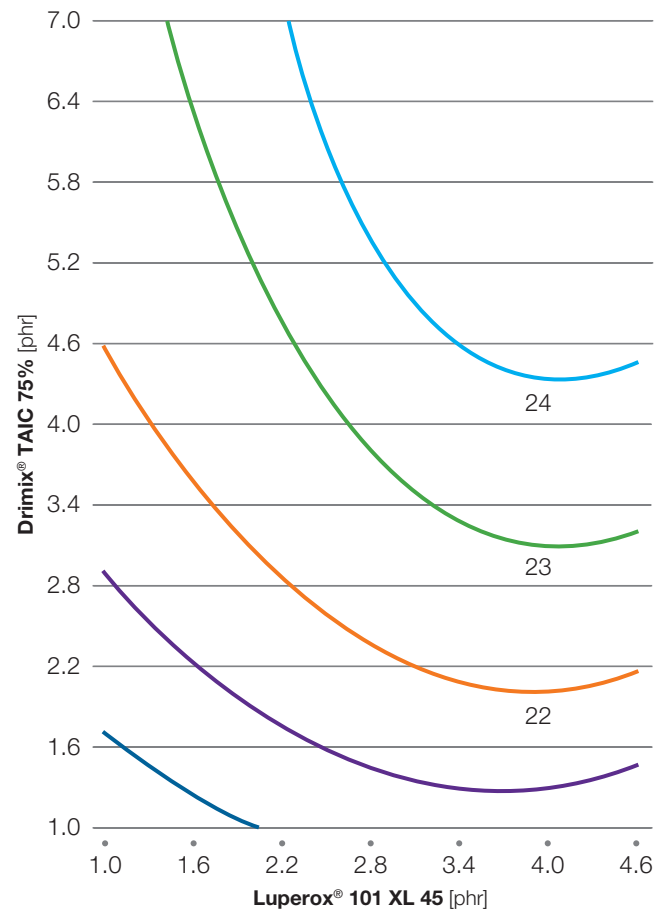


# Tecnoflon® P 757

Peroxide Curable Terpolymer

## Elongation at break [%]

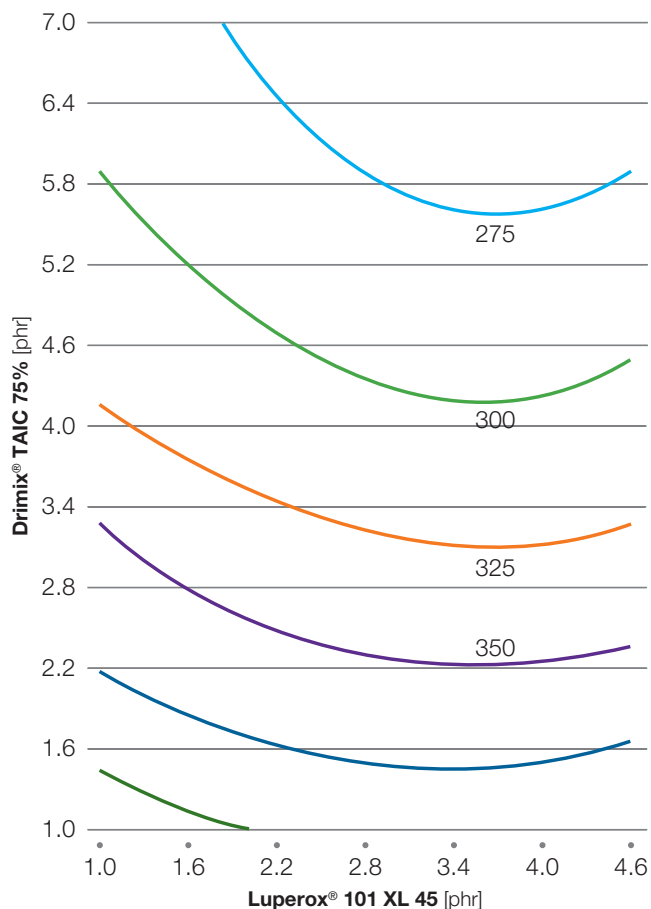

## Hardness [ShoreA]

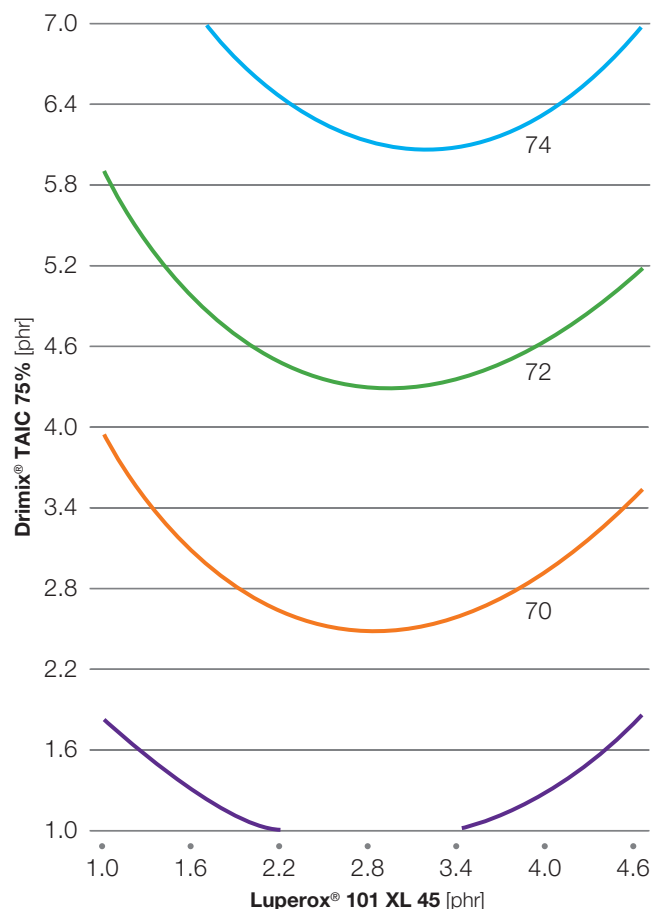

## Fluid resistance

Property	Typical Value	Unit	Test Method
<b>Fuel B, 70 h at 23°C</b>			
Δ Tensile strength	-6	%	
Δ Elongation at break	-6	%	
Δ Hardness	1	Shore A	
Δ Volume	2	%	
<b>Methanol, 70 h at 23°C</b>			
Δ Tensile strength	-53	%	
Δ Elongation at break	-51	%	
Δ Hardness	-21	Shore A	
Δ Volume	83	%	
<b>M15 (Fuel C/Methanol 85/15%), 70 h at 23°C</b>			
Δ Tensile strength	-31	%	
Δ Elongation at break	-26	%	
Δ Hardness	-9	Shore A	
Δ Volume	18	%	

# Tecnoflon® P 757

## Peroxide Curable Terpolymer

Property	Typical Value	Unit	Test Method
<b>IRM 903, 70 h at 150 °C</b>			
Δ Tensile strength	15	%	
Δ Elongation at break	-2	%	
Δ Hardness	3	Shore A	
Δ Volume	0	%	
<b>IRM 903, 168 h at 150 °C</b>			
Δ Tensile strength	6	%	
Δ Elongation at break	-6	%	
Δ Hardness	3	Shore A	
Δ Volume	0	%	
<b>Engine coolants (Prestone), 70 h at 150 °C</b>			
Δ Tensile strength	-8	%	
Δ Elongation at break	-9	%	
Δ Hardness	0	Shore A	
Δ Volume	3	%	
<b>Engine coolants (Prestone), 168 h at 150 °C</b>			
Δ Tensile strength	-11	%	
Δ Elongation at break	-9	%	
Δ Hardness	0	Shore A	
Δ Volume	3	%	
<b>ATF Dexron III, 70 h at 150 °C</b>			
Δ Tensile strength	15	%	
Δ Elongation at break	-2	%	
Δ Hardness	2	Shore A	
Δ Volume	0	%	
<b>ATF Dexron III, 168 h at 150 °C</b>			
Δ Tensile strength	-8	%	
Δ Elongation at break	-9	%	
Δ Hardness	3	Shore A	
Δ Volume	0	%	
<b>ATF Dexron III, 336 h at 150 °C</b>			
Δ Tensile strength	3	%	
Δ Elongation at break	-9	%	
Δ Hardness	3	Shore A	
Δ Volume	0	%	

# Tecnoflon® P 757

## Peroxide Curable Terpolymer

Property	Typical Value	Unit	Test Method
<b>ATF Dexron III, 500 h at 150 °C</b>			
Δ Tensile strength	4	%	
Δ Elongation at break	-6	%	
Δ Hardness	4	Shore A	
Δ Volume	0	%	
<b>ATF Dexron III, 1,000 h at 150 °C</b>			
Δ Tensile strength	-1	%	
Δ Elongation at break	-18	%	
Δ Hardness	5	Shore A	
Δ Volume	0	%	
<b>SH motor oil (Quaker State 5 W – 30 W), 70 h at 150 °C</b>			
Δ Tensile strength	7	%	
Δ Elongation at break	2	%	
Δ Hardness	6	Shore A	
Δ Volume	0	%	
<b>SH motor oil (Quaker State 5 W – 30 W), 168 h at 150 °C</b>			
Δ Tensile strength	8	%	
Δ Elongation at break	2	%	
Δ Hardness	3	Shore A	
Δ Volume	1	%	
<b>Synthetic gear (Mobil SHC 634), 70 h at 150 °C</b>			
Δ Tensile strength	1	%	
Δ Elongation at break	-3	%	
Δ Hardness	1	Shore A	
Δ Volume	1	%	
<b>Synthetic gear (Mobil SHC 634), 168 h at 150 °C</b>			
Δ Tensile strength	1	%	
Δ Elongation at break	-2	%	
Δ Hardness	0	Shore A	
Δ Volume	1	%	
<b>Synthetic gear (Mobil SHC 634), 336 h at 150 °C</b>			
Δ Tensile strength	3	%	
Δ Elongation at break	1	%	
Δ Hardness	1	Shore A	
Δ Volume	1	%	

# Tecnoflon® P 757

Peroxide Curable Terpolymer

## Low temperature properties

Property	Typical Value	Unit	Test Method
TR <sub>10</sub>	-15	°C	ASTM D1329

## Cold brittleness test

Property	Typical Value	Unit	Test Method
<b>Press cure: 6 min at 170 °C, post cure: 24 h at 230 °C</b>			
Brittleness temperature	-34	°C	ASTM D2137

## Gehman's torsional brittleness test

Property	Typical Value	Unit	Test Method
<b>Press cure: 6 min at 170 °C</b>			
T <sub>2</sub>	-15	°C	ASTM D1053
T <sub>5</sub>	-18	°C	
T <sub>10</sub>	-20	°C	
T <sub>100</sub>	-25	°C	
<b>Post cure: 1 h at 230 °C</b>			
T <sub>2</sub>	-11	°C	ASTM D1053
T <sub>5</sub>	-15	°C	
T <sub>10</sub>	-18	°C	
T <sub>100</sub>	-23	°C	
<b>Post cure: 24 h at 230 °C</b>			
T <sub>2</sub>	-11	°C	ASTM D1053
T <sub>5</sub>	-15	°C	
T <sub>10</sub>	-17	°C	
T <sub>100</sub>	-24	°C	



# Tecnoflon® P 757

## Peroxide Curable Terpolymer

### Food processing compounds

Tecnoflon® P 757 is registered in the FDA Inventory of Effective Food Contact Substances (FCS) Notifications, being the subject of Food Contact Notification (FCN #127), with an effective date July 21, 2001. See the list of effective notifications for FCN available on the Agency's web site at:

<http://www.accessdata.fda.gov/scripts/fdcc/?set=FCN>

The finished compounds are intended for repeated use as components of gaskets or seals used in food processing equipment intended to contact food Types I through VII as described in Table 1 of 21 CFR 176.170(c) as follows:

**Table 1:** Types of Raw and Processed Foods

- I. Nonacid, aqueous products; may contain salt or sugar or both (pH above 5.0)
- II. Acid, aqueous products; may contain salt or sugar or both, and including oil-in-water emulsions of low- or high-fat content
- III. Aqueous, acid or nonacid products containing free oil or fat; may contain salt, and including water-in-oil emulsions of low- or high-fat content
- IV. Dairy products and modifications:
  - A Water-in-oil emulsions, high- or low-fat
  - B Oil-in-water emulsions, high- or low-fat
- V. Low-moisture fats and oil
- VI. Beverages:
  - A Containing up to 8 percent of alcohol
  - B Non-alcoholic
  - C Containing more than 8 percent alcohol
- VII. Bakery products other than those included under Types VIII or IX of this table:
  - A Moist bakery products with surface containing free fat or oil
  - B Moist bakery products with surface containing no free fat or oil
- VIII. Dry solids with the surface containing no free fat or oil (no end test required)
- IX. Dry solids with the surface containing free fat or oil

Data for establishing compliance with the FDA standards for Tecnoflon® P 757 based compounds were obtained from cured items having the formulation shown below:

<b>Tecnoflon® P 757</b>	<b>100 phr</b>
Luperox® 101 (98%)	1.35 phr
TAIC (100%)	3 phr

Extraction tests were performed on slabs that were presscured for 10 min at 170 °C, followed by an oven post-cure of 24 h at 200 °C.

### Compounding guidelines for food processing

To design FDA compliant compounds, some restrictions have to be taken into account as far as the curatives, the fillers and the process aids are concerned.

#### 1. Curatives

the following restrictions apply in terms of curatives amount:

<b>Tecnoflon® P 757</b>	<b>100 phr</b>
Luperox® 101 (98%)	≤ 1.35 phr
TAIC (100%)	≤ 3 phr

#### 2. Fillers

The following fillers are approved for use in items intended for repeated food contact use, under 21 CFR 177.2600, section v., and provide at the same time excellent processing behavior and physical properties:

- Barium sulfate
- Silica
- Titanium dioxide
- Carbon black  
(channel process or furnace combustion process; total carbon black not to exceed 50 % by weight of rubber product; furnace combustion black content not to exceed 10 % by weight of rubber products intended for use in contact with milk or edible oils)

#### 3. Process aids

- Carnauba wax
- Struktol® HT 290  
(concentration must not exceed 5% by weight of the rubber compound)

# Tecnoflon® P 757

Peroxide Curable Terpolymer

## Food processing compounds

Test Compound	Typical Value	Unit	Test Method
<b>Tecnoflon® P 757</b>	100	phr	
Luperox® 101 liquid (98 %)	1	phr	
TAIC liquid (98 %) – DIAK 7	3	phr	
TiO <sub>2</sub> (Ti-Pure® R-960)	3	phr	
BaSO <sub>4</sub> (Blanc Fixe HD 80)	70	phr	
Carnauba wax	0.5	phr	

Property	Typical Value	Unit	Test Method
Mooney viscosity ML (1+10') at 121 °C	55.6	MU	ASTM D1646
<b>MDR 12 min at 160 °C arc 3°</b>			ASTM D6601
Minimum torque	1.65	lb·in	
Maximum torque	24.2	lb·in	
t <sub>s2</sub>	0.8	min	
t' <sub>50</sub>	1.5	min	
t' <sub>90</sub>	2.7	min	
<b>Post cure: 4 h at 230 °C</b>			
100% modulus	5,5	MPa	ASTM D412C
Tensile strength	15.1	MPa	
Elongation at break	260	%	
Hardness	69	Shore A	ASTM D2240
<b>Compression set</b> 25% deformation, O-ring #214			ASTM D395 method B
70 h at 200 °C	25	%	

[www.solvay.com](http://www.solvay.com)

[SpecialtyPolymers.EMEA@solvay.com](mailto:SpecialtyPolymers.EMEA@solvay.com) | Europe, Middle East and Africa

[SpecialtyPolymers.Americas@solvay.com](mailto:SpecialtyPolymers.Americas@solvay.com) | Americas

[SpecialtyPolymers.Asia@solvay.com](mailto:SpecialtyPolymers.Asia@solvay.com) | Asia Pacific

Safety Data Sheets (SDS) are available by emailing us or contacting your sales representative. Always consult the appropriate SDS before using any of our products. Neither Solvay Specialty Polymers nor any of its affiliates makes any warranty, express or implied, including merchantability or fitness for use, or accepts any liability in connection with this product, related information or its use. Some applications of which Solvay's products may be proposed to be used are regulated or restricted by applicable laws and regulations or by national or international standards and in some cases by Solvay's recommendation, including applications of food/feed, water treatment, medical, pharmaceuticals, and personal care. Only products designated as part of the Solviva® family of biomaterials may be considered as candidates for use in implantable medical devices. The user alone must finally determine suitability of any information or products for any contemplated use in compliance with applicable law, the manner of use and whether any patents are infringed. The information and the products are for use by technically skilled persons at their own discretion and risk and does not relate to the use of this product in combination with any other substance or any other process. This is not a license under any patent or other proprietary right. All trademarks and registered trademarks are property of the companies that comprise Solvay Group or their respective owners.

© 2015 Solvay Specialty Polymers. All rights reserved. R 02/02/2015 | Version 2.2 Design by ahlersheinel.com