



SOLVAY

asking more from chemistry®

NOCOLOK®



NOCOLOK® Li Flux

New Brazing Flux with
Improved Residue Performance

Improved Residue Performance

Controlled Atmosphere Brazing (CAB) with potassium fluoroaluminate fluxes continues to be a worldwide standard technology used for the production of all-aluminium heat exchangers. It has been demonstrated, by means of corrosion testing methods (e.g., SWAAT; CASS, NSS), that a residual flux layer improves the corrosion resistance when compared with bare parts¹.

However, under certain laboratory conditions the exposure of brazed aluminium substrates to low flow rate (stationary) aqueous media over an extended period of time can potentially lead to specific surface reactions². The main factors involved in such interactions are flux residue solubility and dissolution.

To address this issue, Solvay Fluor has developed a new NOCOLOK[®] composition with improved flux residue performance. When using the new flux, potential surface interactions of brazed aluminium with water are significantly reduced.

The new NOCOLOK[®] Li Flux shows the same outstanding properties and brazing performance of standard potassium fluoroaluminate flux – with further enhancement of the post braze flux residue characteristics.

Test 1 Brazing


Clad aluminium coupons (3003/4343) brazed with NOCOLOK[®] Flux and NOCOLOK[®] Li Flux.

Heating up (569 °C)


Dwelling (605 °C)

Freezing (540 °C)


Coupons without angle,
NOCOLOK[®] Flux
10g/m²

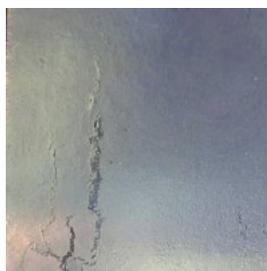

Coupons without angle,
NOCOLOK[®] Li Flux
10g/m²

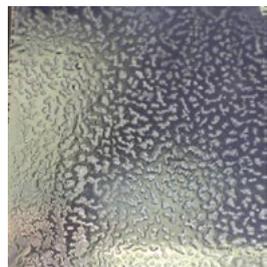

Coupons with angle,
NOCOLOK[®] Flux
10g/m²

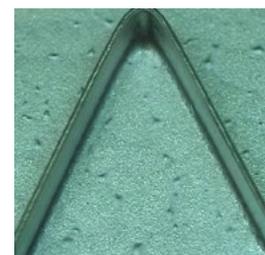

Coupons with angle,
NOCOLOK[®] Li Flux
10g/m²




Notice that the breakup of the oxide layer at 605 °C seems to be more efficient with NOCOLOK[®] Li Flux.

¹ "Influence of Residual Flux Level on the Corrosion behavior of CAB Alloys." A. Gray et. al. International Aluminium Brazing Congress, Dusseldorf; 2002.

² "Study on the Hydrolysis of Post-Braze Flux Residues" P.García and H. Swidersky. 13th Invitational International Aluminum Brazing Seminar, Novi; 2008.

Test 2
Post-Braze Flux
Residue Morphology


SEM micrographs of clad aluminium coupons (3003/4343) brazed with 5g/m²:
 NOCOLOK[®] Flux NOCOLOK[®] Li Flux

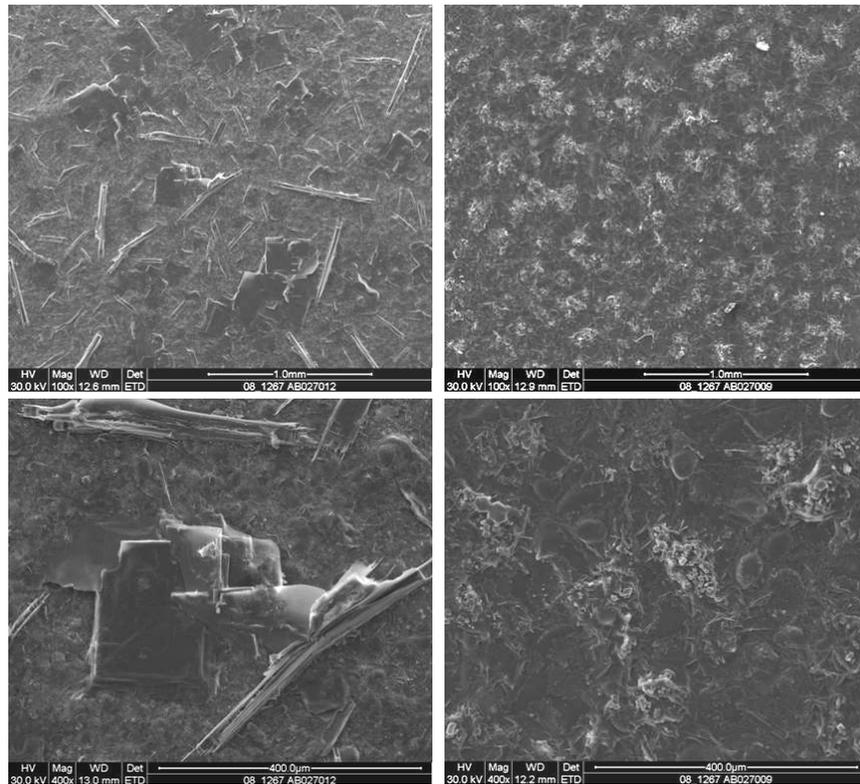

Test 3
Soaking in Water

Soaking tests carried out with de-ionized water show the improvement of post-braze surface integrity. This can be seen in form of a white precipitate suspended in the test water due to the presence of aluminium hydroxide.

Angle-on-Coupons brazed with flux, after 20 days kept in de-ionized water.
 NOCOLOK[®] Flux NOCOLOK[®] Li Flux

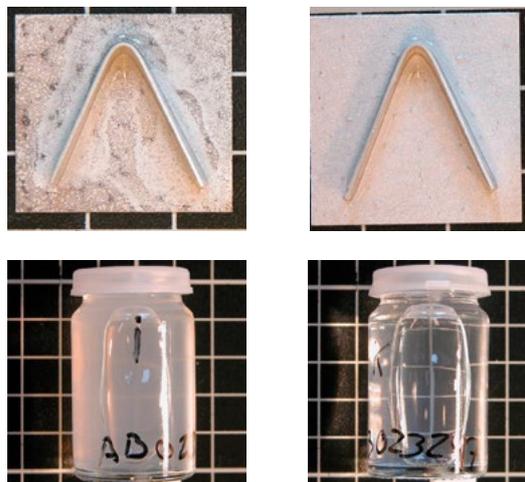

The chemical analyses of the resulting aqueous suspension confirm the lower concentration of flux residue and corrosion products.

	F (ppm)	K (ppm)	Al (ppm)
NOCOLOK [®] Flux	586	1186	1221
NOCOLOK [®] Li Flux	41	423	65

Table 1: Element analyses of water suspension from soaking tests.


Test 4 SWAAT

	Mass Loss %	Pit Max. Depth μm	Pit Number Mean Value
Without Flux	9	340	19
NOCOLOK® Flux	5	210	4
NOCOLOK® Li Flux	3.5	165	3


Table 2: SWAAT after 288 h.

High contrast microscope photographs (magnification 50 times) of aluminium coupons (3003/4343 clad) – after standard brazing cycle and 288h SWAAT:


Coupon sample brazed
without Flux

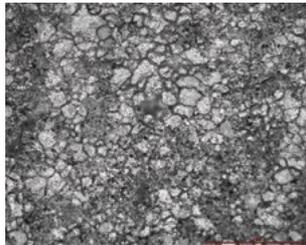

with NOCOLOK® Flux

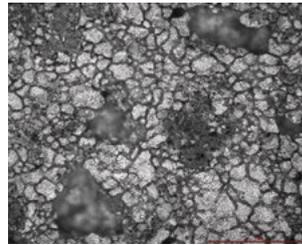

with NOCOLOK® Li Flux

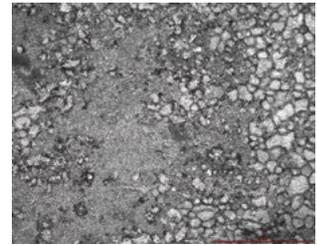

The aluminum coupons (AA3003 with 4343 clad) were fluxed with loads ranging from 3 to 7 g/m². All samples were subjected to a standard cycle under CAB conditions with maximum temperature at 600 °C. The coupons were placed in the furnace without an aluminum angle. After cooling, they were collected, weighted and placed in the SWAAT chamber for a test with an acetic acid/sodium chloride solution.

Immediately after removing the samples from the corrosion chamber, they were cleaned first by gently brushing the surface under cold running water to remove the bulk of the salts and corrosion products. The samples were then immersed in cold concentrated nitric acid (70 %) for 30 minutes, followed by another cold water rinse and then air dried. Nitric acid dissolved the corrosion products without attacking the metal.

The pit depth was calculated by microscope method (i.e. measuring the difference of focus-plane from coupon surface to the bottom of the pit).



Europe
Solvay Fluor GmbH
Postfach 220
30002 Hannover, Germany
Telephone: +49 511 857-0
Fax: +49 511 857-2146

North America
Solvay Fluorides, LLC
3333 Richmond Avenue
Houston, TX 77098, USA
Telephone: +1 713 525-6000
Fax: +1 713 525-7805

Asia/Pacific
Solvay
EWAH University
Industry Building 4th Fl.
150, Bukahyun-ro,
Soedaemun-ku
Seoul 120-140 Korea
Telephone: +82 2 2125 5306
Fax: +82 2 2125 5380

www.solvay.com
www.nocolok.com

Disclaimer:

All statements, information, and data given herein are believed to be accurate and reliable but are presented without guarantee, warranty or responsibility of any kind, express or implied. Statements or suggestions concerning possible use of our products are made without representation or warranty that any such use is free of patent infringement, and are not recommendations to infringe any patent. The user should not assume that all safety measures are indicated, or that other measures may not be required. In any case, the user is not exempt from observing all legal, administrative and regulatory procedures relating to the product, personal hygiene, and protection of human welfare and the environment.